



Brussels, 8 November 2016

## TM 1010:2016

# Determination of the post expansion of an OCF<sup>1</sup> Canister Foam

### 1. Scope

This method describes how to measure the expansion of a freshly dispensed liquid foam (froth) during the curing phase.

### 2. Short description of procedure

The foam is dispensed into a linear joint up to a defined level. The foam expands during the curing phase to its final volume. The post expansion is the volume increase expressed as a percentage of the original dispensed froth.

### 3. Background and purpose

The evaporation of propellants and, in case the of polyurethanes, the generation of CO<sub>2</sub>, expands the froth to a larger volume. This expansion can cause waste of foam and other unwanted effects, which are hard to anticipate. By calculating the post expansion factor, the consumer can estimate the necessary filling degree of the froth to avoid overexpansion.

### 4. Equipment

- 2 moulds (or more depending on the foam – see 5.2 k) made of non-porous material; size 1000 mm x 35 mm x 35 mm (length, height, width). The moulds must not be deformed by the foam during the curing period (recommended thickness 20 mm if no further fixation applied).
- Sharp cutter.
- Caliper, accuracy 1 mm.
- Controlled climate chamber.
- Adhesive tape.
- Paper, length > 1000 mm.

### 5. Procedure

#### 5.1 Preparation

- a) Test conditions: 23 °C, 50 % r. h. (norm climate).

---

<sup>1</sup> **OCF**: Generic term for moisture-curing One-Component Foams dispensed from pressurised containers ("aerosol cans") as well as self-curing two-component foams dispensed from pressurised containers ("1.5 component foams").

- b) Bring the test canister to the test temperature for at least 24 h.
- c) Prepare two moulds where each consists of two plates and two spacers with a width of 35 mm (Figure 1).
- d) Place the first mould onto the paper.

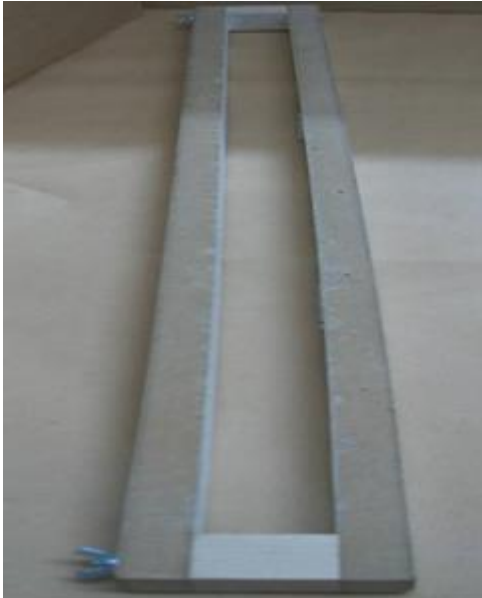


Figure 1: Lower mould before application



Figure 2: Setup with foam after application

## 5.2 Experimental procedure

- e) Shake the canister vigorously 20 times.
- f) Discard the first 50 g of foam.
- g) Apply the foam exactly up to the top edge of the mould ( $h_0 = 35$  mm).
- h) Dispensing the foam should take approximately 15- 20sec with a constant speed.
- i) Placed the second (empty) mould on top of the filled mould (Fig. 2).
- j) In the case of highly expanding foams, more moulds may be necessary in order to avoid expansion over the top of the mould.
- k) Let the foam cure for 24 h.
- l) Remove the upper mould with the help of the knife.
- m) Measure the height of cured foam in seven points by the use of range finder or caliper ( $h_1$ ). The measuring points should be always in the same position e. g. every 100 mm (Figure 3 and figure 4).

**Note: If the boards were bent during the curing phase, the test must be repeated with stronger boards.**

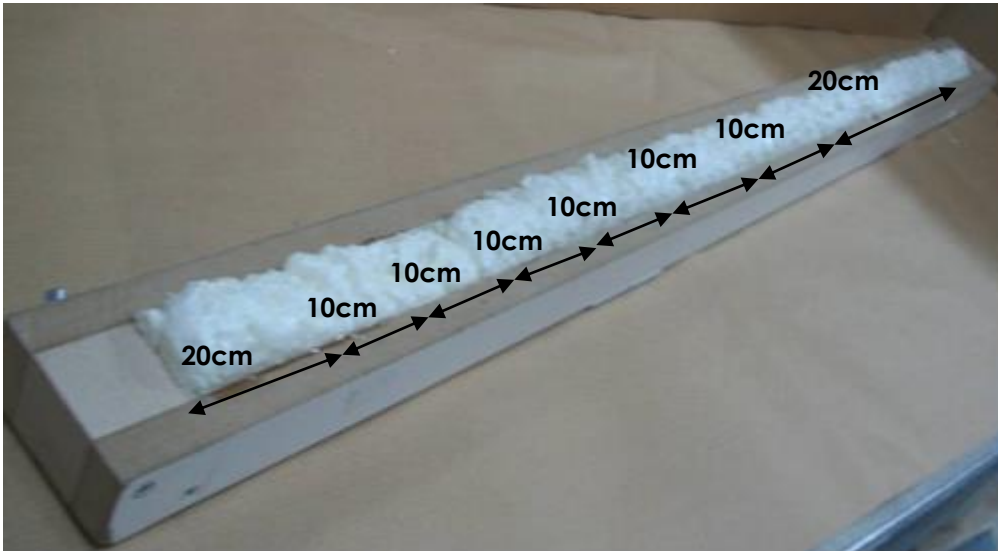


Fig. 3: Foam ready to be measured

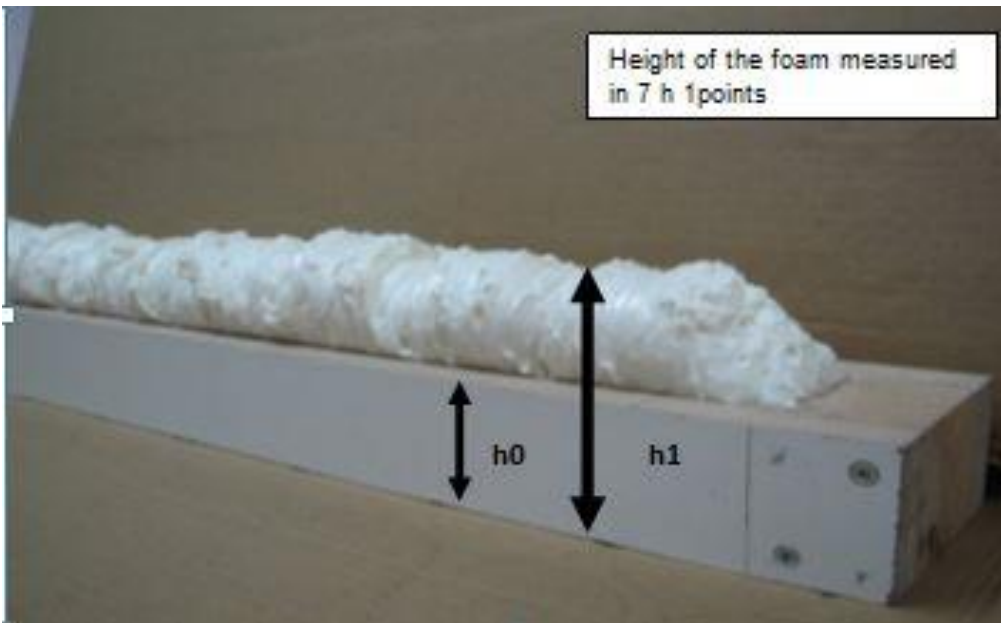


Fig. 4: Foam ready for measurement

### 5.3 Evaluation

The post expansion is calculated with following formula:

$$PE (\%) = \frac{h1 - h0}{h0} * 100$$

where:

PE(%) is the Post Expansion [%]

h0 is the height of the mould [mm]

h1 is the mean height (from 5 points) of the foam after curing [mm] where two extremes values from 7 measuring points are eliminated.

## 6. Revision

Version	Date	Remarks
2	8 November 2016	Revised and checked by FEICA

## 7. Contact

FEICA – Association of the European Adhesive & Sealant Industry  
Avenue Edmond van Nieuwenhuyse, 4  
B- 1160 Brussels, Belgium  
Tel: +32 (0)2 676 73 20 | Fax: +32 (0)2 676 73 99  
[info@feica.eu](mailto:info@feica.eu) | [www.feica.eu](http://www.feica.eu)

**FEICA**, the Association of the European Adhesive & Sealant Industry is a multinational association representing the European Adhesive and Sealant Industry. With the support of its national associations and several direct and affiliated members, FEICA coordinates, represents and advocates the common interests of our industry throughout Europe. In this regard FEICA aims at establishing a constructive dialogue with legislators in order to act as a reliable partner to resolve issues affecting the European Adhesive and Sealant Industry.

**Publication ref.: TM-1010:2016**

**Copyright ©FEICA, 2016**

*Reproduction is authorised provided the source is fully acknowledged in the form: 'Source: FEICA TM-1010:2016, <http://www.feica.eu>'.*

*This document has been designed using the best knowledge currently available, and is to be relied upon at the user's own risk. The information is provided in good faith and no representations or warranties are made with regards to the accuracy or completeness, and no liability will be accepted for damages of any nature whatsoever resulting from the use or reliance on this paper. This document does not necessarily represent the views of all member companies of FEICA.*